


OFFICE OF NAVAL RESEARCH

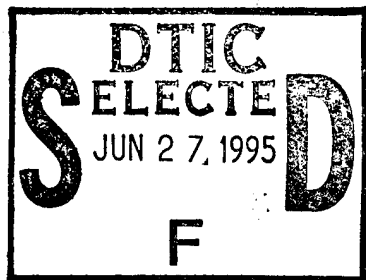

Contract N00014-92-J-1433

R & T Code 4132038

Technical Report No. 25

Exploring Factors that Determine Cis/Trans Structure and Tacticity in Polymers Prepared by  
Ring Opening Metathesis Polymerizations Involving Initiators of the Type Syn and Anti  
 $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})(\text{OR})_2$ . Observation of a Temperature Dependent Cis/Trans Ratio

by

R. R. Schrock, J.-K. Lee, R. O'Dell, J. H. Oskam

in press

in

*Macromolecules*

Department of Chemistry 6-331  
Massachusetts Institute of Technology  
Cambridge, Massachusetts 02139

June 14, 1995

DTIC QUALITY INSPECTED 3

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

19950626 048

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)

2. REPORT DATE

6-14-95

3. REPORT TYPE AND DATES COVERED

Technical Report

4. TITLE AND SUBTITLE

Exploring Factors that Determine Cis/Trans Structure and Tacticity in Polymers Prepared by Ring Opening Metathesis Polymerizations Involving Initiators of the Type Syn and Anti Mo(NAr)(CHCMe<sub>2</sub>Ph)(OR)<sub>2</sub>. Observation of a Temperature Dependent Cis/Trans Ratio

5. FUNDING NUMBERS

Contract N00014-92-J-1433  
R&T Code 4132038

6. AUTHOR(S)

R. R. Schrock, J.-K. Lee, R. O'Dell, J. H. Oskam

Kenneth Wynne

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)

Massachusetts Institute of Technology  
Department of Chemistry, 6-331  
77 Massachusetts Avenue  
Cambridge, MA 02139

8. PERFORMING ORGANIZATION  
REPORT NUMBER

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)

Department of the Navy  
Office of Naval Research  
800 North Quincy Street  
Arlington, VA 22217-5000

10. SPONSORING/MONITORING  
AGENCY REPORT NUMBER

25

11. SUPPLEMENTARY NOTES

12a. DISTRIBUTION AVAILABILITY STATEMENT

Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.

12b. DISTRIBUTION CODE

13. ABSTRACT (Maximum 200 words)

The factors that determine the structure (cis/trans and tacticity) of polymers prepared by ring opening metathesis polymerization (ROMP) using well-defined initiators of the type Mo(NAr)(CHCMe<sub>2</sub>Ph)(OR)<sub>2</sub> (Aryl = a substituted aryl group and OR = a variety of alkoxides) have been explored. The main finding is a dependence of cis/trans structure on temperature; at low temperatures (-35°C) all cis polymer is formed and at high temperatures (65°C) up to 90% trans polymers are formed. These results are consistent with formation of cis polymer from syn alkylidene rotamers and trans polymer from anti alkylidene rotamers in circumstances where syn and anti rotamers can interconvert.

14. SUBJECT TERMS

15. NUMBER OF PAGES

16. PRICE CODE

17. SECURITY CLASSIFICATION  
OF REPORT

Unclassified

18. SECURITY CLASSIFICATION  
OF THIS PAGE

Unclassified

19. SECURITY CLASSIFICATION  
OF ABSTRACT

Unclassified

20. LIMITATION OF ABSTRACT

UL

Exploring Factors that Determine Cis/Trans Structure and Tacticity in Polymers Prepared by  
 Ring Opening Metathesis Polymerizations With Initiators of the Type  
 Syn and Anti  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})(\text{OR})_2$ .  
 Observation of a Temperature Dependent Cis/Trans Ratio.

by

Richard R. Schrock,\* Jin-Kyu Lee, Richard O'Dell, and John H. Oskam

Department of Chemistry 6-331  
 Massachusetts Institute of Technology  
 Cambridge, MA 02139


|                    |                                     |
|--------------------|-------------------------------------|
| Accession For      |                                     |
| NTIS CRA&I         | <input checked="" type="checkbox"/> |
| DTIC TAB           | <input type="checkbox"/>            |
| Unannounced        | <input type="checkbox"/>            |
| Justification      |                                     |
| By                 |                                     |
| Distribution /     |                                     |
| Availability Codes |                                     |
| Dist               | Avail and/or Special                |
| A-1                |                                     |

**Abstract**

The factors that determine the structure (cis/trans and tacticity) of polymers prepared by ring opening metathesis polymerization (ROMP) from 2,3-bis-(trifluoromethyl)norbornadiene (NBDF6) and several dicarboalkoxynorbornadienes using well-defined initiators of the type  $\text{Mo}(\text{NAryl})(\text{CHCMe}_2\text{Ph})(\text{OR})_2$  (Aryl = a substituted aryl group and OR = a variety of alkoxides) have been explored. The main finding is a dependence of cis/trans structure on temperature; at low temperatures ( $-35^\circ\text{C}$ ) all cis polymer is formed and at high temperatures ( $65^\circ\text{C}$ ) up to 90% trans polymers are formed. These results are consistent with formation of cis polymer from syn alkylidene rotamers and trans polymer from anti alkylidene rotamers in circumstances where syn and anti rotamers can interconvert. Several all cis polymers prepared from achiral initiators that contain various fluorinated alkoxides were found to be biased toward isotacticity. In one case, however, the polymer was biased toward syndiotacticity.

## INTRODUCTION



Ring opening metathesis polymerization (ROMP) is a method of making polymers from a wide variety of cyclic olefins.<sup>1,2</sup> If the olefins are relative reactive compared to ordinary olefins (e.g., norbornenes and norbornadienes), and "well-defined" initiators are employed, then the polymerization can be living.<sup>3,4</sup> Well-defined initiators for polymerizations of this type that have been used often are complexes of the type  $\text{Mo}(\text{NAryl})(\text{CHCMe}_2\text{Ph})(\text{OR})_2$  (Aryl = a substituted aryl group such as 2,6- $\text{Me}_2\text{C}_6\text{H}_3$ ).<sup>5</sup> A feature of such species, and perhaps classical metathesis catalysts also,<sup>1</sup> is the presence of syn and anti alkylidene rotamers that may, or may not, interconvert readily compared to the rate of polymerization (equation 1). We recently proposed<sup>6</sup> that syn and anti rotamers of complexes of this type play a major role in determining

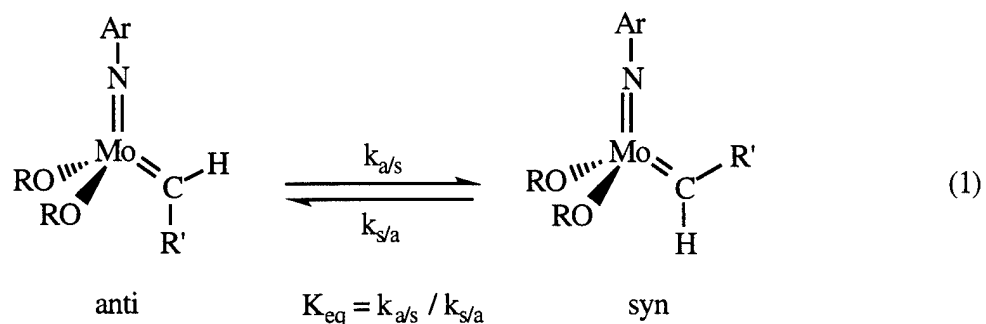

whether ROMP polymers prepared from several norbornenes or norbornadienes<sup>4,7,8</sup> contain cis or trans double bonds. Syn and anti rotamers whose reactivities could be evaluated ( $\text{OR} = \text{OCMe}(\text{CF}_3)_2$ ) were found to have vastly different reactivities and to interconvert at rates that differed by up to six orders of magnitude, relatively rapidly ( $k_{s/a} = 1 \text{ s}^{-1}$  at  $25^\circ$ ) when  $\text{OR} = \text{O}-t\text{-Bu}$ , but relatively slowly ( $k_{s/a} = 10^{-5} \text{ s}^{-1}$  at  $25^\circ$ ) when  $\text{OR} = \text{OCMe}(\text{CF}_3)_2$ . In most cases that were examined  $K_{\text{eq}}$  was found to be  $>10^3$ . The rate of rotamer interconversion was found to be faster by approximately three orders of magnitude in *ortho*-monosubstituted phenyl imido complexes such as  $\text{Mo}(\text{N}-2-t\text{-Bu}-\text{C}_6\text{H}_4)(\text{CH}-t\text{-Bu})[\text{OCMe}(\text{CF}_3)_2]_2$  than in 2,6-disubstituted phenylimido complexes.<sup>6</sup> The single bulky substituent in the *ortho* position was proposed to

promote bending of the imido ligand and therefore a lowering of the barrier to rotamer interconversion by making the orbital that lies in the N-Mo-C plane, the one that is believed to stabilize an alkylidene in the process of rotating  $180^\circ$ , more readily accessible.

The monomer that has been employed often in investigations of this general type is 2,3-bis(trifluoromethyl)norbornadiene (NBDF6). On the basis of detailed NMR studies<sup>6</sup> it was proposed that  $\text{syn-Mo}(\text{NAr})(\text{CH-t-Bu})[\text{OCMe}(\text{CF}_3)_2]_2$  ( $\text{Ar} = 2,6\text{-i-Pr}_2\text{C}_6\text{H}_3$ ) reacts with NBDF6 by coordinating to the exo face of the unsubstituted double bond to generate a  $\text{syn}$  first insertion product having a  $\text{cis}$  double bond ( $\text{syn}+1_c$ ; equation 2), while the  $\text{anti}$  rotamer reacts (at least 100 times more rapidly) to give a  $\text{syn}$  first insertion product having a  $\text{trans}$  double bond ( $\text{syn}+1_t$ ; equation 3).  $\text{Trans-poly}(\text{NBDF6})$  prepared from  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})(\text{O-t-Bu})_2$

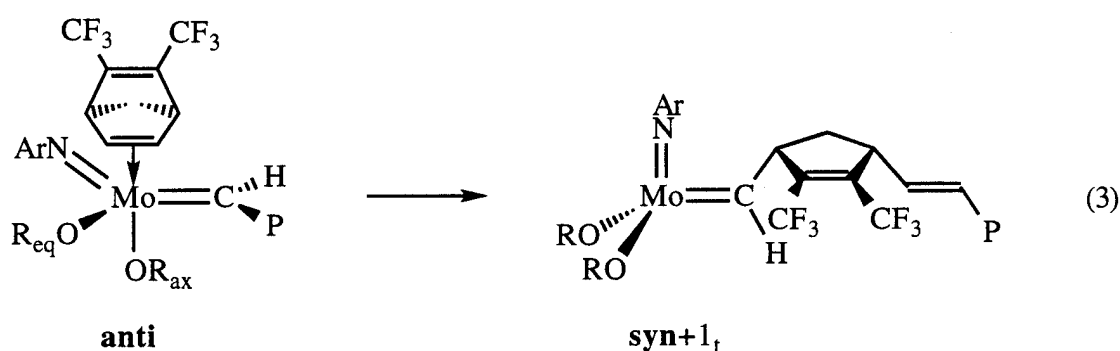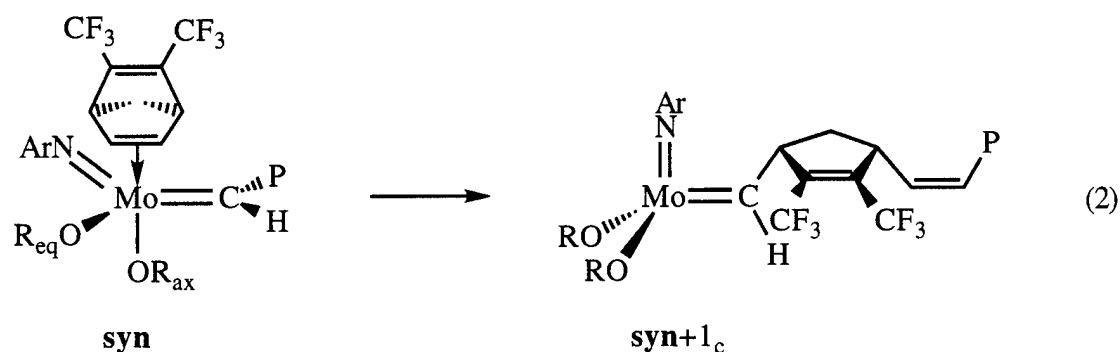

was proposed to arise from reactions involving only (unobservable)  $\text{anti}$  rotamers, since the  $\text{anti}$  rotamer is kinetically accessible at room temperature ( $k_{s/a} \approx 1 \text{ s}^{-1}$ ; equation 1), and since studies involving  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OCMe}(\text{CF}_3)_2]_2$  suggest that the  $\text{anti}$  rotamer is much more

reactive than the syn rotamer. Since  $K_{eq} \approx 10^3$  the anti rotamer actually must be at least  $10^5$  more reactive than the syn rotamer in order to generate >99% trans double bonds.<sup>6</sup> On the other hand, use of  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OCMe}(\text{CF}_3)_2]_2$  as the initiator gave cis-poly(NBDF6).<sup>9</sup> In this case syn-Mo(NAr)(CHCMe<sub>2</sub>Ph)[OCMe(CF<sub>3</sub>)<sub>2</sub>]<sub>2</sub>, the predominant species present in solution at 25°, is reactive enough to react with NBDF6. Since a syn insertion product that contains a cis double bond is formed at each step the polymer continues to grow from syn rotamers to give all-cis poly(NBDF6). Anti rotamers of alkylidene intermediates, even though they are much more reactive, are simply *inaccessible* on the time scale of the polymerization reaction in the OCMe(CF<sub>3</sub>)<sub>2</sub> system.

Tacticity is believed to be a separate issue, at least in systems that have been explored so far. The four possible regular primary structures of polynorbornene (for purposes of illustration) are shown in Scheme 1. It is believed that a molybdacyclobutane complex is formed when the monomer approaches one of the two CNO faces of the pseudo-tetrahedral catalyst (equation 2 or 3). The two CNO faces correspond to the two sides of the Mo=C bond. If the monomer approaches the same CNO face in each step, an isotactic polymer is formed; if the monomer approaches alternate CNO faces sequentially, a syndiotactic polymer is formed. If a polymerization process yields all trans or all cis polymer, then it is possible in some cases to determine the degree of tacticity in a relatively simple manner by <sup>13</sup>C NMR.<sup>1</sup> Recently it has become possible to prepare highly tactic all cis polymers with molybdenum initiators that contain a racemic binaphtholate ligand<sup>10</sup> and to prove that related all cis polymers that contain chiral groups in the ester of a dicarboalkoxynorbornadiene are isotactic while all trans polymers that contain chiral groups in the ester of a dicarboalkoxynorbornadiene are syndiotactic.<sup>7</sup> It also has been shown that all cis polymers prepared from several enantiomerically pure 2,3-disubstituted norbornenes employing molybdenum binaphtholate initiators are isotactic.<sup>7</sup>


Molybdenum alkylidene complexes that contain phenoxide ligands have been relatively little studied. Unlike complexes that contain t-butoxide ligands, both syn and anti rotamers are often observable and they interconvert with activation energies between 15 and 18 kcal

mol<sup>-1</sup>.<sup>11,12</sup> Molybdenum phenoxide complexes that have been briefly investigated as ROMP initiators were found to produce polymers that contain both cis and trans double bonds. On the other hand, "linked" phenoxide ligands such as binaphtholates and biphenolates often give rise to highly cis and highly tactic ROMP polymers.<sup>7,10</sup> In order to explore the origin of cis and trans polymers we chose to examine phenoxide initiators in this paper. In order to explore how the tacticity of some all cis polymers varies with the monomer, the imido ligand, and the alkoxide ligand, we chose to examine polymers prepared with Mo(NAr)(CHCMe<sub>2</sub>Ph)(OR)<sub>2</sub> initiators where OR = OMe(CF<sub>3</sub>)<sub>2</sub>, OC(CF<sub>3</sub>)<sub>3</sub>, or OC(CF<sub>3</sub>)<sub>2</sub>(CF<sub>2</sub>CF<sub>2</sub>CF<sub>3</sub>).

## RESULTS

### Molybdenum 2-t-Butylphenylimido Complexes

We suspected that the rate of rotamer interconversion in molybdenum initiators that contain the 2-t-butylphenylimido ligand would be in an "intermediate" range where changes in temperature might dramatically effect the outcome of the polymerization reaction. An initiator that can be purified by recrystallization is most desirable, so Mo(N-2-t-Bu-C<sub>6</sub>H<sub>4</sub>)(CH-t-Bu)(OAr)<sub>2</sub>,<sup>13</sup> an oil, is unsuitable. Mo(N-2-t-Bu-C<sub>6</sub>H<sub>4</sub>)(CHCMe<sub>2</sub>Ph)(OR)<sub>2</sub> compounds where R = 2-t-Bu-C<sub>6</sub>H<sub>4</sub> or 2,4-t-Bu<sub>2</sub>C<sub>6</sub>H<sub>3</sub> were also found to be oils,<sup>14</sup> but Mo(N-2-t-Bu-C<sub>6</sub>H<sub>4</sub>)(CHCMe<sub>2</sub>Ph)(BiphenoBu<sub>4</sub>) (BiphenoBu<sub>4</sub> = 2,2'-[4,4',6,6'-t-Bu<sub>4</sub>](C<sub>6</sub>H<sub>2</sub>)<sub>2</sub>O<sub>2</sub>)<sup>15,16</sup> could be prepared as a crystalline THF adduct, **1**(THF). THF could be removed in vacuo from a sample of **1**(THF) dissolved in a high boiling, non-coordinating solvent such as toluene, and THF-free **1** thereby obtained. **1**, **1**(THF), and several related new and known crystalline

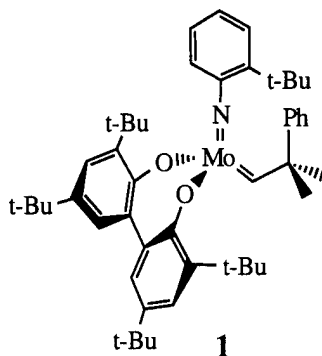

initiators used in this work are listed in Table 1.

The  $^1\text{H}$  NMR spectrum of **1** at  $23^\circ\text{C}$  showed one sharp alkylidene resonance at 10.87 ppm, while the  $^{13}\text{C}$  NMR spectrum showed one sharp alkylidene resonance at 279 ppm with a value for  $^1J_{\text{CH}}$  (120 Hz) characteristic of a syn rotamer.<sup>5,6</sup> No significant change was observed upon cooling the sample to  $-65^\circ\text{C}$ . However, the proton NMR spectrum of **1**(THF) in toluene- $d_8$  at  $26^\circ\text{C}$  showed a broad alkylidene  $\text{H}_\alpha$  resonance at 11.03 ppm (Figure 1). When the NMR sample of **1**(THF) was cooled, two new alkylidene resonances grew in at 14.08 ppm and 12.85 ppm (Figure 1) and sharpened at the expense of the 11.03 ppm resonance upon further cooling, ultimately to give a spectrum containing two alkylidene resonances in a 1:3 ratio. Addition of THF ( $\sim 10$  equiv) to a sample of **1** in toluene- $d_8$  at  $-65^\circ\text{C}$  generated a sample having the same two alkylidene resonances found in the spectrum of **1**(THF) at low temperature. Therefore we propose that the  $\text{H}_\alpha$  resonances at 14.08 and 12.85 ppm are due to THF adducts of anti and syn rotamers, respectively, i.e., **1**<sub>anti</sub>(THF) and **1**<sub>syn</sub>(THF). (It is well-documented that  $\text{H}_\alpha$  resonances in alkylidene complexes in this family move downfield upon adduct formation, and that anti  $\text{H}_\alpha$  resonances are found downfield of syn  $\text{H}_\alpha$  resonances.<sup>5</sup>) The two unidentified tiny resonances at 12.78 and 14.00 ppm observed near the resonances for **1**<sub>anti</sub>(THF) and **1**<sub>syn</sub>(THF) could not be identified. They could possibly be structural isomers in which THF coordinates to the metal in a position other than what is believed to be the favored CNO face.<sup>6</sup> As the temperature of the sample containing **1**<sub>anti</sub>(THF) and **1**<sub>syn</sub>(THF) is raised, THF appears to come off the syn rotamer more readily than the anti rotamer, as judged by broadening of the 12.85 ppm resonance first at  $-15^\circ\text{C}$  (Figure 1) and loss of intensity as  $K_{\text{eq}}$  shifts toward the THF-free complex. At higher temperatures all resonances coalesce into a single broad alkylidene  $\text{H}_\alpha$  resonance between 11.0 and 11.1 ppm as the equilibrium shifts virtually entirely toward the base-free form of **1** and THF exchange is rapid on the NMR time scale.

Samples of **1** were photolyzed at  $-75^\circ\text{C}$  in toluene in an attempt to produce an observable amount of **1**<sub>anti</sub>. (Photolysis has been found to cause interconversion of syn and anti rotamers of  $\text{Mo}^6$  and  $\text{Re}^{17}$  alkylidene rotamers.) However, no **1**<sub>anti</sub> accumulated after 18h of photolysis.



Either back reaction of  $1_{\text{anti}}$  to  $1_{\text{syn}}$  (photochemical or thermal) is too fast on the chemical time scale at  $-75^{\circ}\text{C}$ , or photolysis is not an effective method of effecting anti/syn interconversion in phenoxide complexes. The former seems more likely to be the case, in part since bending of the mono-substituted phenylimido ligand is known to reduce the barrier to alkylidene rotation significantly in  $\text{OCMe}(\text{CF}_3)_2$  complexes.<sup>6</sup> Therefore we suspect that  $1_{\text{syn}}$  and  $1_{\text{anti}}$  can equilibrate on the chemical time scale even at  $-75^{\circ}\text{C}$  and that the equilibrium lies well toward the syn rotamer.

It is interesting to note that for the analogous 2,6-diisopropylphenylimido complex ( $3(\text{THF})$ ; Table 1) the anti:syn ratio is 1:3 at room temperature in toluene- $d_8$ . (On the basis of chemical shifts it is likely that the anti form is the THF adduct and the syn form the THF-free form of **3**.) Perhaps the additional steric hindrance caused by the 2,6-disubstituted phenyl ring decreases the stability of the THF-free syn rotamer relative to the THF adduct of the anti rotamer in addition to significantly slowing the rate of interconversion of anti and syn forms.

### Polymerizations Employing **1** as the Initiator

Polymerizations of NBDF6 or DCMNBD (2,3-dicarbomethoxynorbornadiene) were carried out with **1** as the initiator in THF, toluene, or dichloromethane (Table 2). In discussing these results we will assume that  $1_{\text{anti}}$  is in equilibrium with  $1_{\text{syn}}$  on a time scale of the order of the polymerization reaction, that trans double bonds are formed only from anti rotamers and cis double bonds only from syn rotamers, and that only pseudo four-coordinate THF-free complexes are reactive.<sup>6</sup> (We will later discuss whether these assumptions are valid.)

The first six entries in Table 2 show data for samples of  $\text{poly}(\text{NBDF6})_{100}$ . Homogeneous polymerizations were observed when THF was employed as a solvent, but in toluene another phase formed as polymerization progressed. Yields were high at room temperature or above, but low at low temperatures, even with a polymerization time of 48 hr. At temperatures below  $-10^{\circ}$  we propose that polymerization is slowed down to a significant degree simply by coordination of THF (competitive inhibition), most strongly to the anti rotamer. (The anti rotamer is known to have a greater affinity for  $\sigma$ -donor bases such as phosphines.<sup>5</sup>) THF therefore selectively

"poisons" the anti rotamer by competing more effectively with the monomer for the coordination site in the anti rotamer than in the syn rotamer. Consequently only cis bonds are produced via syn rotamers at  $-35^{\circ}\text{C}$  since effectively only the THF-free syn alkylidene is accessible. However, the reaction is extremely slow since so little THF-free alkylidene is available. Conversely, at  $65^{\circ}$  THF is dissociating readily to give both anti and syn four-coordinate alkylidene intermediates. Since syn/anti interconversion is believed to be rapid, the majority of the polymer arises via anti intermediates, and 76% trans polymer is formed. Poly(NBDF6) prepared at  $23^{\circ}$  in THF has approximately a 1:1 ratio of trans and cis double bonds. In toluene at  $23^{\circ}$  reaction of the monomer with the anti form is no longer as inhibited by THF as it is at low temperature and the % trans content therefore increases from what it is in pure THF, from 42% to 68% (Table 2).

Polymerization of 2,3-dicarbomethoxynorbornadiene with **1** in toluene yielded analogous results (Table 2). Polymerization at  $-35^{\circ}$  was carried out in dichloromethane in order to enhance solubility of the polymer at that temperature. At  $-35^{\circ}$  a 36% yield of 100% cis polymer was realized in 12 hr. At higher temperatures in toluene the % trans steadily increased to 81% at  $80^{\circ}$ . A control experiment ruled out the possibility that trans polymer results from isomerization of cis double bonds in the polymer (secondary metathesis). All-cis poly(DCMNBD) (100 mer) that had been prepared using **2**(THF) as the initiator<sup>10</sup> was added to the living alkylidene generated by adding 10 equivalents of DCMNBD to **1**, and the mixture was heated for 2h at  $80^{\circ}\text{C}$ . The trans content did not increase to any significant degree, consistent with slow secondary metathesis, even at  $80^{\circ}$ .

In order to confirm that syn and anti rotamer accessibility is the origin of the dependence of polymer structure on temperature, it would be desirable to show that the cis/trans structure of polymers prepared with  $\text{OCMe}(\text{CF}_3)_2$  initiators, where a syn rotamer is known to generate  $\text{syn}+1_{\text{cis}}$  (equation 2) while an anti rotamer generates  $\text{syn}+1_{\text{trans}}$  (equation 3)<sup>6</sup>, is also temperature dependent. It is already known that both syn and anti rotamers of  $\text{OCMe}(\text{CF}_3)_2$  complexes are qualitatively much more reactive in toluene than they are in THF and that the

reactivity of an anti rotamer decreases more significantly in THF than the reactivity of a syn rotamer in THF, relative to their reactivities in toluene.

The best known  $\text{OCMe}(\text{CF}_3)_2$  initiator is  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OCMe}(\text{CF}_3)_2]_2$  (**7**), which generates high cis poly(NBDF6) in toluene or THF at  $25^\circ\text{C}$  (Table 3).<sup>9</sup> At  $65^\circ$  the cis content drops to 88% for poly(NBDF6) prepared in toluene and to 83% for poly(NBDF6) prepared in THF (Table 3), consistent with greater participation of the anti rotamer (to give trans polymer) in reactions at the higher temperatures. Polymerizations employing  $\text{Mo}(\text{N-2-t-BuC}_6\text{H}_4)(\text{CHCMe}_2\text{Ph})[\text{OCMe}(\text{CF}_3)_2]_2$  (**4**) must be carried out at  $-35^\circ\text{C}$  in order to achieve a similarly high cis content because rotamer interconversion in  $\text{Mo}(\text{N-2-t-BuC}_6\text{H}_4)$  complexes is about three orders of magnitude faster than in NAr complexes.<sup>6</sup> When the temperature is raised to  $65^\circ$  the cis content drops to 29%. These results are consistent with the proposal that a higher rate of rotamer interconversion leads to higher trans polymer as a consequence of a greater accessibility of anti rotamers, and that THF reduces the reactivity of an anti rotamer more strongly than a syn rotamer to produce a polymer with a higher cis content compared to a polymer prepared in toluene. Predictably, polymer yields are lower in THF or at low temperatures as a consequence of slow and incomplete polymerization.

Two other new 2,6-diisopropylphenylimido phenoxide initiators (**3** and **5**) were used to make poly(NBDF6)<sub>100</sub> at various temperatures and the results compared with those obtained employing **6** as the initiator (Table 3). The trend of the effect of temperature on cis/trans structure using all three initiators is toward higher trans content of the polymer at higher temperature and in toluene. The formation of predominantly cis polymer employing **3** was expected since the analogous neopentylidene initiator also yields virtually all cis polymer.<sup>6</sup> At  $65^\circ$  some decrease in the cis content is observed, analogous to the results employing **7** (Table 3).

**The Tacticity of High Cis Polymers Prepared from  $\text{Mo}(\text{NAryl})(\text{CHCMe}_2\text{Ph})(\text{OR})_2$  Initiators (OR =  $\text{OCMe}(\text{CF}_3)_2$ ,  $\text{OC}(\text{CF}_3)_3$ , or  $\text{OC}(\text{CF}_3)_2(\text{CF}_2\text{CF}_2\text{CF}_3)$ ).**

The tacticity of all cis or all trans polymers prepared from norbornenes and norbornadienes in many cases can be determined by  $^{13}\text{C}$  NMR methods.<sup>1</sup> For example, the

resonance for what was C(7) in a norbornadiene monomer is often sensitive to the orientation of the five-membered rings on each side of a given ring in the polymer; therefore for an all cis polymer three resonances for C(7) (in an isotactic, a syndiotactic, or an atactic triad (Scheme 1)) are often observed, usually in a nonstatistical fashion. Additional structure is usually attributed to sensitivity of C(7) to structural variations beyond the triad level. In this section we examine how tacticity varies with the alkoxide and monomer for initiators which lead to high cis polymers. In some cases polymers begin to precipitate during the course of the polymerization reaction, but so far we have found that a heterogeneous polymerization reaction (e.g., in toluene) does not yield results (in terms of PDI, cis content, or tacticity) that are significantly different from those found for a homogeneous reaction (e.g., in THF). We will assume that all polymerizations described here that give rise to a polymer with a high cis content and low PDI are living, although that has not been proven in every case. In several cases the reaction time has been doubled or trebled without consequence in terms of cis content or PDI, consistent with slow secondary metathesis reactions. The yields of all polymerization reactions are high.

In Figure 2a is shown the C(7) resonances in the  $^{13}\text{C}$  spectrum of high cis (98%) poly(NBDF6)<sub>200</sub> (PDI = 1.10; Table 4) prepared using **7** as the initiator in THF.<sup>9</sup> On the basis of analogous polymers prepared from dicarboalkoxynorbornadiene monomers that contain chiral groups in the ester<sup>7</sup> it has been suggested that the most downfield C(7) resonance is in a ring in a m,m or isotactic triad. The bias toward isotacticity is a consequence of some chain end control. Virtually the same result is obtained for poly(NBDF6) prepared in toluene (run 2, Table 4; Figure 2b). (The additional structure on the isotactic resonance for C(7) at ~38.5 ppm is most likely ascribable to a sensitivity to structure beyond the triad level.) Polymers prepared in solvent mixtures (runs 3 and 4; Table 4) are analogous to those prepared in runs 1 and 2. The % mm triads drops slightly (from 62% in run 2 to 52% in run 11) when Mo(N-2,6-Me<sub>2</sub>C<sub>6</sub>H<sub>3</sub>)(CHCMe<sub>2</sub>Ph)[OCMe(CF<sub>3</sub>)<sub>2</sub>]<sub>2</sub> is employed as the initiator.

Polymerization of NBDF6 by the Mo(NAr)(CHCMe<sub>2</sub>Ph)[OC(CF<sub>3</sub>)<sub>3</sub>]<sub>2</sub> initiator in toluene (run 5, Table 4) produces a virtually all cis polymer that contains only ~40% isotactic triads

(Figure 2c), while polymer produced by the  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OC}(\text{CF}_3)_2(\text{CF}_2\text{CF}_2\text{CF}_3)]_2$  initiator (run 10) produces a high cis polymer that contains 77% *syndiotactic* triads (Table 4, Figure 2d). There is no way to rationalize such results on the basis of our present knowledge of these catalyst systems. The effect of several solvents on the resulting polymer prepared from the  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OC}(\text{CF}_3)_3]_2$  initiator was minimal (runs 6 through 9). Polymers prepared from N-2,6- $\text{Me}_2\text{C}_6\text{H}_3$  or N-2-t-Bu $\text{C}_6\text{H}_4$  initiators (runs 11 through 14) again were between 52 and 88% *isotactic*. The contrast between the syndiotacticity of the polymer prepared in run 10 and the isotacticity of the polymer prepared in run 13 is dramatic. The fact that polymer prepared in run 14 is still virtually all cis, and therefore most likely arises from syn rotamers, is interesting in view of the fact that the rate of syn to anti conversion is probably approximately three orders of magnitude higher than the rate of syn to anti conversion in a complex that contains a NAr or a N-2,6- $\text{Me}_2\text{C}_6\text{H}_3$  ligand.<sup>6</sup>


Polymerization of dicarbomethoxynorbornadiene by  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OCMe}(\text{CF}_3)_2]_2$  gives essentially an all cis polymer whose  $^{13}\text{C}$  NMR spectrum in the C(7) region (Figure 3a) is similar to the spectrum of poly(NBDF6) shown in Figure 2a, except the three C(7) resonances in poly(dicarbomethoxynorbornadiene) are closer together than they are in poly(NBDF6). It has been argued that both polymers are biased toward isotacticity (mm).<sup>7</sup> The poly(dicarbomethoxynorbornadiene) prepared with the F9 and F13 initiators (runs 16 and 17) is essentially the same as that in run 15. Similar polymers are prepared with an initiator that contains the N-2,6- $\text{Me}_2\text{C}_6\text{H}_3$  ligand (runs 18, 19, 20). The dramatic change in tacticity observed in the sequence of runs 2, 5, and 10, but not runs 15, 16, and 17, suggests that tacticity can sensitively depend upon the nature of the monomer, and at the same time, of course, the intermediate alkylidenes formed from it in the polymerization reaction.

Polymerization of ethyl, isopropyl, and t-butyl dicarboalkoxynorbornadiene derivatives (runs 21 - 25) yields high cis polymers whose  $^{13}\text{C}$  NMR spectra (Figure 3b, c, d) in the region of the resonance for C(7) appear to be analogous to that for the dicarbomethoxy derivative (Figure 3a). However, we cannot be certain that the spectrum shown in Figure 3d can be ascribed to

highly isotactic polymer, i.e., that the *rm/mr* C(7) resonance does not simply overlap with the *mm* C(7) resonance to give what only appears to be highly isotactic polymer. The results shown in Table 4 (runs 23, 24, 25) make the assumption that no C(7) resonances overlap. If this is true then there would appear to be some tendency toward isotacticity as the size of the alkyl group in the dicarboalkoxynorbornadiene derivative increases.

## DISCUSSION

The most important result reported here is that the *cis/trans* structure of ROMP polymers is temperature dependent in a manner that is consistent with the proposed equilibrium between a less active *syn* form (that gives *cis* polymer) and a more reactive *anti* form (that gives *trans* polymer), as shown in equation 4. Confirmation would require detailed knowledge of the

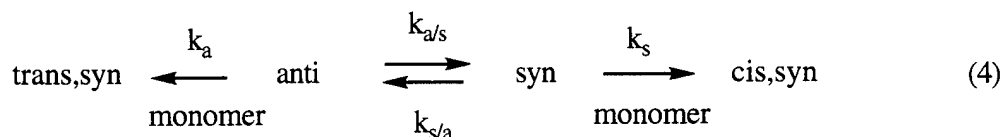

temperature dependencies of the rates of the first order reactions,  $k_{a/s}[\text{anti}]$  and  $k_{s/a}[\text{syn}]$ , as well as the second order propagation reactions,  $k_a[\text{anti}][\text{monomer}]$  and  $k_s[\text{syn}][\text{monomer}]$ . Unfortunately, none actually is known. Nevertheless, circumstances that would give rise to the observed result can be imagined, in part because the temperature dependencies of the first order reactions (rotamer interconversion) and second order reactions (reactions with monomer) are likely to be significantly different;  $\Delta S^\ddagger$  for the second order propagation reactions should be relatively large and negative, which should lead to a less dramatic dependence of the rate on temperature, as shown in Figure 4. Therefore at low temperatures the polymer chain can grow more rapidly than *syn* and *anti* rotamers can interconvert. Since the predominant rotamer (in the absence of THF) is *syn*, and the reaction between a *syn* rotamer and monomer is proposed to produce a *syn* rotamer, polymerization at low temperature in toluene or dichloromethane would give rise to *cis* polymer, as observed. In THF at low temperature the *anti* form can be observed,

but it binds THF more strongly. The syn rotamer, which dissociates THF more readily than the anti rotamer, therefore becomes the more reactive. Above the "crossover" point (the temperature where the rates of rotamer interconversion and chain growth are equal, at some monomer concentration) equilibration of syn and anti rotamers becomes fast relative to chain growth, so ultimately chain growth is rate limiting,  $k_a[\text{anti}][\text{monomer}]$  is roughly of the same magnitude as  $k_s[\text{syn}][\text{monomer}]$ , and both cis and trans polymers form.

The circumstance shown in equation 4 is analogous to the situation encountered in catalytic asymmetric hydrogenation of amino acid precursors by cationic rhodium catalysts.<sup>18</sup> In that case the enantiomeric product that is observed near room temperature arises via reaction of molecular hydrogen with the unobservable minor rhodium diastereomer. A significant difference between the Rh system and the system discussed here (in the *absence* of a coordinating solvent) is that the two diastereomeric rhodium complexes equilibrate via loss and recoordination of substrate, not a simple first order interconversion as proposed here. Nevertheless, at low temperatures (or high dihydrogen pressures) interconversion of rhodium diastereomeric complexes cannot compete with reaction of the "wrong" (major) rhodium complex with dihydrogen, and the observed ee consequently decreases. (It is assumed that the chirality of the product that results from the major diastereomer is opposite that arising from the minor diastereomer.)

A good example of a "crossover" of the rate of first and second order reactions with temperature is the "trapping" of an alkyl hydride intermediate in a rhodium hydrogenation catalyst system.<sup>19</sup>

Some confirmation of the proposed behavior of syn and anti rotamers of  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OCMe}(\text{CF}_3)_2]_2$  for forming cis and trans polymers, respectively, is the polymerization of 1,7,7-trimethylnorbornene.<sup>20,21</sup> The (extremely slow) rate of polymerization is independent of monomer concentration, the observed rate constant corresponds to the value for  $k_{s/a}$ , and the polymer that is formed contains trans double bonds, all consistent with chain growth via anti rotamers. Apparently 1,7,7-trimethylnorbornene is so bulky that it does not react with

syn-Mo(NAr)(CHCMe<sub>2</sub>Ph)[OCMe(CF<sub>3</sub>)<sub>2</sub>]<sub>2</sub>, but it does react rapidly with anti-Mo(NAr)(CHCMe<sub>2</sub>Ph)[OCMe(CF<sub>3</sub>)<sub>2</sub>]<sub>2</sub>. Since a syn form is the result of the reaction between an anti form and monomer, the slow conversion of a syn form to an anti form becomes the rate limiting step in this particular polymerization reaction. This result emphasizes the extent to which the nature of the monomer can change the mechanism of polymerization. It also illustrates that selective formation of a syn rotamer from *either* a syn or anti rotamer is a key feature that leads to the observed phenomena.

Unfortunately, none of what we propose in equation 4 can be confirmed independently for phenoxide-containing initiators, since we cannot measure rotamer interconversion or test relative reactivities of syn and anti rotamers. Therefore, we cannot discount the possibility that both cis and trans polymers can form from only the syn rotamer, or even both syn and anti rotamers, and that cis selectivity simply breaks down at higher temperatures. It should be noted that even if the source of cis and trans double bonds in these ROMP polymers is what we propose, there is some indication that the arylimido functionality plays a major role in directing the approach of the monomer to the CNO face of the propagating alkylidene, and therefore that selectivity will not be independent of the imido group.<sup>6</sup>

We have found all cis polymers prepared by a variety of achiral initiators to be biased toward giving isotactic polymers by chain end control. However, it is not possible at this stage to rationalize the degree of isotacticity, or why it reverses in one case (run 10). Ideally we would have to know (via molecular mechanics calculations) the relative ease of a given monomer approaching the two faces of the syn-Mo=C bond in the living alkylidene formed from a given monomer. That possibility does not seem likely in the near future.

## EXPERIMENTAL PROCEDURES

All experiments were performed under a nitrogen atmosphere in a Vacuum Atmospheres drybox or by standard Schlenk techniques unless otherwise specified. Reagent grade diethyl ether and tetrahydrofuran were distilled from sodium benzophenone ketyl under nitrogen. Polymerization grade THF was vacuum transferred twice from sodium benzophenone ketyl.



Polymerization grade toluene was stored over NaK alloy and passed through alumina prior to use.

HPLC grade solvents were used in Gel permeation chromatography (GPC) runs and were degassed prior to use. GPC was carried out using a Waters Ultrastaygel 10573, Shodex KF-802.5, 803, 804, 805, and 800P columns, a Viscotek Differential Refractometer / Viscometer H-500, and a Spectroflow 757 absorbance detector on a samples 0.1 - 0.3% (w/v) in THF which were filtered through a Millex-SR 0.5  $\mu$ m filter in order to remove particulates. GPC columns were calibrated versus polystyrene standards (Polymer Laboratories Ltd.) which ranged from MW = 1260 -  $2.75 \times 10^6$ . NMR data were obtained at 300 MHz and are listed in parts per million downfield from tetramethylsilane. Chemical shifts vary somewhat from sample to sample in the case of THF adducts, perhaps as a consequence of some chemical shift dependence on concentration and temperature. Spectra were obtained at 25°C unless otherwise noted. Elemental analyses (C, H, N) were performed on a Perkin-Elmer 2400 CHN analyzer.

All the chemicals used were reagent grade and purified by standard methods. Benzaldehyde was purchased from Aldrich, and was distilled over Na and pass over alumina before use.  $\text{Mo}(\text{N}-2\text{-t-BuC}_6\text{H}_4)(\text{CHCMe}_2\text{Ph})(\text{OTf})_2(\text{DME})^{13}$ ,  $\text{Mo}(\text{N}-2\text{-t-BuC}_6\text{H}_4)(\text{CHCMe}_2\text{Ph})[\text{OCMe}(\text{CF}_3)_2]_2^{13}$  (4),  $\text{Mo}(\text{N}-2,6\text{-Me}_2\text{C}_6\text{H}_3)(\text{CHCMe}_2\text{Ph})[\text{Bipheno}(\text{t-Bu})_4]^{10}$  (2),  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})(\text{O}-2\text{-t-Bu-C}_6\text{H}_4)_2^{12}$  (5),  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OCMe}_2(\text{CF}_3)]_2^{13}$  (6),  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OCMe}(\text{CF}_3)_2]_2^{22}$  (7),  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OC}(\text{CF}_3)_3]_2^{13}$  and  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{OC}(\text{CF}_3)_2(\text{CF}_2\text{CF}_2\text{CF}_3)]_2^{13}$  were prepared as described in the literature.

$\text{Mo}(\text{N}-2\text{-t-Bu-C}_6\text{H}_4)(\text{CHCMe}_2\text{Ph})[\text{Bipheno}(\text{t-Bu})_4](\text{THF})$  [1(THF)].  $\text{K}_2[\text{Bipheno}(\text{t-Bu})_4] \cdot \text{THF}$  (390 mg, 0.70 mmol), prepared from 4,4',6,6'-tetra-*t*-butyl-2,2'-biphenol and KO-*t*-Bu, was added as a solid to the pre-cooled (-30°C) solution of  $\text{Mo}(\text{N}-2\text{-t-Bu-C}_6\text{H}_4)(\text{CHCMe}_2\text{Ph})(\text{OTf})_2(\text{DME})$  (500 mg, 0.65 mmol) in 50 mL of THF. The mixture was stirred for 6h and the solvent was removed in vacuo. The residue was dissolved in  $\text{CH}_2\text{Cl}_2$  and the insoluble potassium salts were removed by filtration. The filtrate was concentrated and

layered with pentane in order to crystallize the product; yield 0.38 g (68%):  $^1\text{H}$  NMR (toluene- $d_8$ )  $\delta$  11.03 (br s, 1,  $\text{H}_\alpha$ ), 7.80-6.70 (m, 13,  $\text{H}_{\text{aryl}}$ ), 3.55 (m, 4,  $\text{OCH}_2\text{CH}_2$ ), 1.86 (s, 3,  $\text{CH}_3$ ), 1.61 (s, 9,  $\text{CMe}_3$ ), 1.47 (s, 9,  $\text{CMe}_3$ ), 1.44 (m, 4,  $\text{OCH}_2\text{CH}_2$ ), 1.31 (s, 9,  $\text{CMe}_3$ ), 1.28 (s, 9,  $\text{CMe}_3$ ), 1.24 (s, 3,  $\text{CH}_3$ ), 1.17 (s, 9,  $\text{CMe}_3$ );  $^1\text{H}$  NMR (toluene- $d_8$ ,  $-60^\circ\text{C}$ )  $\delta$  14.08 (s, anti  $\text{H}_\alpha$ ), 12.85 (s, syn  $\text{H}_\alpha$ ); partial  $^{13}\text{C}$  NMR (toluene- $d_8$ ,  $-60^\circ\text{C}$ )  $\delta$  311.2 ( $\text{CHCMe}_2\text{Ph}$ , anti), 299.5 ( $\text{CHCMe}_2\text{Ph}$ , syn).

**$\text{Mo}(\text{N-2-t-Bu-C}_6\text{H}_4)(\text{CHCMe}_2\text{Ph})[\text{Bipheno}(\text{t-Bu})_4]$  (1).** The THF-free complex was obtained quantitatively as a dark-red powder by dissolving **1(THF)** in toluene and removing all solvent in vacuo:  $^1\text{H}$  NMR (toluene- $d_8$ )  $\delta$  10.87 (s, 1,  $\text{H}_\alpha$ ), 7.80-6.75 (m, 13,  $\text{H}_{\text{aryl}}$ ), 1.87 (s, 3,  $\text{CH}_3$ ), 1.61 (s, 9,  $\text{CMe}_3$ ), 1.47 (s, 9,  $\text{CMe}_3$ ), 1.30 (s, 9,  $\text{CMe}_3$ ), 1.28 (s, 9,  $\text{CMe}_3$ ), 1.17 (s, 9,  $\text{CMe}_3$ ), 1.14 (s, 3,  $\text{CH}_3$ );  $^{13}\text{C}$  NMR (toluene- $d_8$ )  $\delta$  279.9 (d,  $^1J_{\text{CH}} = 120$ ,  $\text{CHCMe}_2\text{Ph}$ ), 156.7, 155.9, 153.0, 151.9, 144.8, 144.7, 141.7, 141.6, 132.9, 132.3, 129.7, 128.9, 128.8, 127.3, 126.7, 126.6, 126.5, 126.3, 126.0 ( $\text{C}_{\text{aryl}}$ ), 55.2 ( $\text{CMe}_2\text{Ph}$ ), 37.0 ( $\text{CMe}_3$ ), 36.6 ( $\text{CMeMePh}$ ), 35.8 ( $\text{CMeMePh}$ ), 35.2 ( $\text{CMe}_3$ ), 35.1 ( $\text{CMe}_3$ ), 33.3 ( $\text{CMe}_3$ ), 32.1 ( $\text{CMe}_3$ ), 32.0 ( $\text{CMe}_3$ ), 31.9 ( $\text{CMe}_3$ ), 31.0 ( $\text{CMe}_3$ ), 30.4 ( $\text{CMe}_3$ ). Anal. Calcd for  $\text{C}_{48}\text{H}_{65}\text{NO}_2\text{Mo}$ : C, 73.54; H, 8.36; N, 1.79. Found: C, 73.87; H, 8.18; N, 1.51.

**$\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})[\text{Bipheno}(\text{t-Bu})_4](\text{THF})$  [**3(THF)**].** The synthesis was similar to that of **1(THF)** employing  $\text{Mo}(\text{NAr})(\text{CHCMe}_2\text{Ph})(\text{OTf})_2(\text{DME})$  in place of  $\text{Mo}(\text{N-2-t-Bu-C}_6\text{H}_4)(\text{CHCMe}_2\text{Ph})(\text{OTf})_2(\text{DME})$ :  $^1\text{H}$  NMR ( $\text{C}_6\text{D}_6$ )  $\delta$  14.06 (s, anti  $\text{H}_\alpha$ ), 11.46 (s, 1, syn  $\text{H}_\alpha$ ), 7.80-6.90 (m, 12,  $\text{H}_{\text{aryl}}$ ), 3.81 (sept, 2,  $\text{CHMe}_2$ ), 3.52 (br s, 2,  $\text{OCH}_2\text{CH}_2$ ), 1.90 (s, 3,  $\text{CH}_3$ ), 1.60 (d, 6,  $\text{CHMe}_2$ ), 1.55 (s, 18,  $\text{CMe}_3$ ), 1.42 (s, 3,  $\text{CH}_3$ ), 1.29 (br s, 13,  $\text{CMe}_3$  and  $\text{OCH}_2\text{CH}_2$ ), 1.20 (s, 9,  $\text{CMe}_3$ ), 0.96 (d, 6,  $\text{CHMe}_2$ ). Anal. Calcd for  $\text{C}_{54}\text{H}_{77}\text{NO}_3\text{Mo}$ : C, 73.36; H, 8.78; N, 1.58. Found: C, 73.23; H, 9.49; N, 1.43.

**Polymerization reactions.** The following is a typical procedure. A solution of NBDF6 (310 mg, 1.36 mmol) in 4 mL of toluene was added to a solution of **4** (10.0 mg, 13.6  $\mu\text{mol}$ ) in 1 mL of toluene and the mixture was heated to  $65^\circ\text{C}$  in an oil bath. After 5h at  $65^\circ\text{C}$  benzaldehyde (14.0  $\mu\text{L}$ , 134  $\mu\text{mol}$ , 10 equiv) was added to react with any alkylidene present. The mixture was

stirred for 1h and the polymer was precipitated in methanol and dried in vacuo to give 300 mg of polymer (97%). For polymerizations at low temperature, a pre-cooled (-35°C) solution containing the monomer was added to the cold solution of the initiator and the mixture was kept at approximately -35°C in the drybox freezer. The mixture was stirred several times during the polymerization reaction.

**Acknowledgements.** R.R.S. thanks the Navy for supporting research on ring opening metathesis polymerization.

## References

- (1) Ivin, K. J. "Olefin Metathesis"; Academic Press: New York, 1983.
- (2) Grubbs, R. H.; Tumas, W. *Science* **1989**, *243*, 907.
- (3) Schrock, R. R. *Acc. Chem. Res.* **1990**, *23*, 158.
- (4) Schrock, R. R. in "Ring-Opening Polymerization"; D. J. Brunelle, Ed.; Hanser: Munich, 1993; pp 129.
- (5) Feldman, J.; Schrock, R. R. *Prog. Inorg. Chem.* **1991**, *39*, 1.
- (6) Oskam, J. H.; Schrock, R. R. *J. Am. Chem. Soc.* **1993**, *115*, 11831.
- (7) O'Dell, R.; McConville, D. H.; Hofmeister, G. E.; Schrock, R. R. *J. Am. Chem. Soc.* **1994**, *116*, 3414.
- (8) Bazan, G.; Khosravi, E.; Schrock, R. R.; Feast, W. J.; Gibson, V. C.; O'Regan, M. B.; Thomas, J. K.; Davis, W. M. *J. Am. Chem. Soc.* **1990**, *112*, 8378.
- (9) Feast, W. J.; Gibson, V. C.; Marshall, E. L. *J. Chem. Soc., Chem. Commun.* **1992**, 1157.
- (10) McConville, D. H.; Wolf, J. R.; Schrock, R. R. *J. Am. Chem. Soc.* **1993**, *115*, 4413.
- (11) Schrock, R. R.; Crowe, W. E.; Bazan, G. C.; DiMare, M.; O'Regan, M. B.; Schofield, M. H. *Organometallics* **1991**, *10*, 1832.
- (12) Schrock, R. R.; Murdzek, J. S.; Bazan, G. C.; Robbins, J.; DiMare, M.; O'Regan, M. J. *Am. Chem. Soc.* **1990**, *112*, 3875.
- (13) Oskam, J. H.; Fox, H. H.; Yap, K. B.; McConville, D. H.; O'Dell, R.; Lichtenstein, B. J.;

Schrock, R. R. *J. Organometal. Chem.* **1993**, 459, 185.

(14) Lee, J.-K. Ph.D. Thesis, Massachusetts Institute of Technology, 1995.

(15) Schaverien, C. J.; Meijboom, N.; Orpen, A. G. *J. Chem. Soc., Chem. Commun.* **1992**, 124.

(16) van der Linden, A.; Schaverien, C. J.; Meijboom, N.; Ganter, C.; Orpen, A. G. *J. Am. Chem. Soc.* **1995**, 117, 3008.

(17) Toreki, R.; Schrock, R. R. *J. Am. Chem. Soc.* **1992**, 114, 3367.


(18) Landis, C. R.; Halpern, J. *J. Am. Chem. Soc.* **1987**, 109, 1746.

(19) Chan, A. S. C.; Halpern, J. *J. Am. Chem. Soc.* **1980**, 102, 838.


(20) Feast, W. J.; Gibson, V. C.; Ivin, K. J.; Kenwright, A. M.; Khosravi, E. *J. Chem. Soc., Chem. Commun.* **1994**, 1399.

(21) Feast, W. J.; Gibson, V. C.; Ivin, K. J.; Kenwright, A. M.; Khosravi, E. *J. Molec. Catal.* **1994**, 90, 87.


(22) Fox, H. H.; Lee, J.-K.; Park, L. Y.; Schrock, R. R. *Organometallics* **1993**, 12, 759.

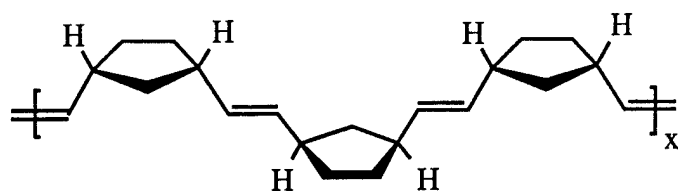


trans, isotactic (*mm*)

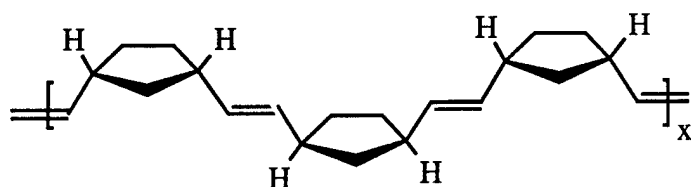

trans, syndiotactic (*rr*)

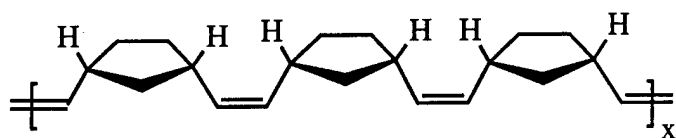

cis, isotactic (*mm*)

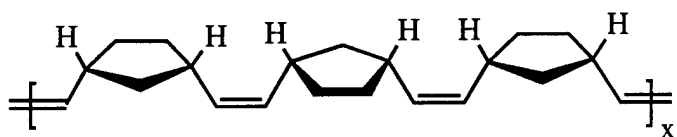

cis, syndiotactic (*rr*)

Scheme 1. The four possible regular primary structures of polynorbornene.

**Table 1.** Crystalline Mo(VI) initiators employed in this work.<sup>a</sup>

| Complex  |               | $\delta(\text{H}_\alpha)^b$ | yield(%) | ref |
|--|---------------|-----------------------------|----------|-----|
| Mo(N-2-t-BuC <sub>6</sub> H <sub>4</sub> )(CHR)[Bipheno(t-Bu) <sub>4</sub> ]   | <b>1</b>      | 10.87                       | --       | -   |
| Mo(N-2-t-BuC <sub>6</sub> H <sub>4</sub> )(CHR)[Bipheno(t-Bu) <sub>4</sub> ](THF)  | <b>1(THF)</b> | 11.15                       | 78       | -   |
| Mo(N-2,6-Me <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHR)[Bipheno(t-Bu) <sub>4</sub> ](THF)  | <b>2(THF)</b> | 11.52 <sup>c</sup><br>14.10 |          | 13  |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHR)[Bipheno(t-Bu) <sub>4</sub> ](THF)  | <b>3(THF)</b> | 11.43 <sup>d</sup><br>14.30 | 68       | -   |
| Mo(N-2-t-BuC <sub>6</sub> H <sub>4</sub> )(CHR)[OCMe(CF <sub>3</sub> ) <sub>2</sub> ] <sub>2</sub>   | <b>4</b>      | 11.79                       | -        | 19  |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHR)(O-2-t-Bu-C <sub>6</sub> H <sub>4</sub> ) <sub>2</sub>  | <b>5</b>      | 11.79 <sup>e</sup><br>13.37 | 91       | -   |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHR)[OCMe <sub>2</sub> (CF <sub>3</sub> )] <sub>2</sub>   | <b>6</b>      | 11.68                       | -        | 19  |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHR)[OCMe(CF <sub>3</sub> ) <sub>2</sub> ] <sub>2</sub>   | <b>7</b>      | 12.12                       | -        | 20  |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHR)[OC(CF <sub>3</sub> ) <sub>3</sub> ] <sub>2</sub>   | <b>8</b>      | 12.12                       | -        | 20  |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHR)[OC(CF <sub>3</sub> ) <sub>2</sub> (CF <sub>2</sub> CF <sub>2</sub> CF <sub>3</sub> )] <sub>2</sub> | <b>9</b>      | 12.12                       | -        | 20  |

(a) R = CMe<sub>2</sub>Ph (b) Values are reported in ppm in C<sub>6</sub>D<sub>6</sub> at ~23°C (c) 88% syn at ~23°C in C<sub>6</sub>D<sub>6</sub>. (d) 75% syn at ~23°C in C<sub>6</sub>D<sub>6</sub>. (e) 93% syn at ~23°C in C<sub>6</sub>D<sub>6</sub>.

**Table 2.** NBDF6 and DCMNBD 100mers prepared employing **1** as the initiator.<sup>a</sup>

| Monomer | T (°C) | solvent                         | time (h) | cis/trans <sup>b</sup> | PDI <sup>c</sup> | yield (%) |
|---------|--------|---------------------------------|----------|------------------------|------------------|-----------|
| NBDF6   | -35    | THF                             | 48       | 100/0                  | --               | ~5        |
| NBDF6   | -10    | THF                             | 48       | 100/0                  | --               | ~5        |
| NBDF6   | 15     | THF                             | 24       | 83/17                  | 1.38             | 43        |
| NBDF6   | 23     | THF                             | 5        | 58/42                  | 1.17             | 90        |
| NBDF6   | 23     | toluene <sup>d</sup>            | 5        | 32/68                  | 1.34             | 98        |
| NBDF6   | 65     | THF                             | 5        | 24/76                  | 1.10             | 99        |
| DCMNBD  | -35    | CH <sub>2</sub> Cl <sub>2</sub> | 12       | 100/0                  |                  | 36        |
| DCMNBD  | 23     | toluene                         | 1        | 54/46                  |                  | 93        |
| DCMNBD  | 50     | toluene                         | 1        | 35/65                  |                  | 96        |
| DCMNBD  | 80     | toluene                         | 1        | 19/81                  |                  | 93        |

(a) NBDF6 = 2,3-bis(trifluoromethyl)norbornadiene; DCMNBD = 2,3-dicarbomethoxynorbornadiene. (b) Measured by <sup>1</sup>H and <sup>13</sup>C NMR as described elsewhere.<sup>3</sup>

(c) In THF versus polystyrene standards. (d) Immiscible phase formed during polymerization. One equivalent of THF present.

**Table 3.** Poly(NBDF6) 100mers prepared with various initiators at various temperatures.

| T (°C)  | solvent | time (h) | cis/trans <sup>a</sup> | PDI <sup>b</sup>  | yield(%)        |
|---|---------|----------|------------------------|-------------------|-----------------|
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHCMe <sub>2</sub> Ph)[OCMe(CF <sub>3</sub> ) <sub>2</sub> ] <sub>2</sub> (7)    |         |          |                        |                   |                 |
| 25  | toluene | 5        | 97/3                   | 1.28 <sup>c</sup> | 100             |
| 65  | toluene | 5        | 88/12                  | 1.29 <sup>c</sup> | 94              |
| 23  | THF     | 5        | 96/4                   | 1.29              | 27 <sup>d</sup> |
| 65  | THF     | 5        | 83/17                  | 1.98              | 45 <sup>d</sup> |
| Mo(N-2-t-BuC <sub>6</sub> H <sub>4</sub> )(CHCMe <sub>2</sub> Ph)[OCMe(CF <sub>3</sub> ) <sub>2</sub> ] <sub>2</sub> (4)                    |         |          |                        |                   |                 |
| -35   | toluene | 24       | 97/3                   | 1.56 <sup>c</sup> | 83              |
| 23  | toluene | 5        | 78/22                  | 1.18              | 100             |
|   | THF     | 5        | 87/13                  | --                | 21 <sup>d</sup> |
| 65  | toluene | 5        | 29/71                  | 1.32 <sup>c</sup> | 97              |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHCMe <sub>2</sub> Ph)[Bipheno(t-Bu) <sub>4</sub> ] (3)                          |         |          |                        |                   |                 |
| -35   | THF     | 48       | --                     | --                | 0               |
| 23  | THF     | 5        | 99/1                   | 1.33              | 98              |
| 65  | THF     | 5        | 90/10                  | 1.19              | 96              |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHCMe <sub>2</sub> Ph)(O-2-t-Bu-C <sub>6</sub> H <sub>4</sub> ) <sub>2</sub> (5) |         |          |                        |                   |                 |
| -35   | THF     | 50       | 78/22                  | --                | 23              |
| 23  | THF     | 5        | 69/31                  | 1.28              | 90              |
|   | toluene | 5        | 65/35                  | 1.82              | 92              |
| 65  | THF     | 5        | 39/61                  | 1.14              | 100             |
| Mo(N-2,6-i-Pr <sub>2</sub> C <sub>6</sub> H <sub>3</sub> )(CHCMe <sub>2</sub> Ph)[OCMe <sub>2</sub> (CF <sub>3</sub> ) <sub>2</sub> ] (6)   |         |          |                        |                   |                 |
| -35   | toluene | 48       | 56/44                  | 1.99              | 63 <sup>d</sup> |
| 23  | toluene | 5        | 36/64                  | 1.24              | 100             |
| 65  | toluene | 5        | 9/91                   | 1.61 <sup>c</sup> | 95              |
| 23  | THF     | 5        | 50/50                  | 1.32              | 50 <sup>d</sup> |
| 65  | THF     | 5        | 13/87                  | 1.34 <sup>c</sup> | 99              |

(a) Measured as described elsewhere.<sup>3</sup> (b) In THF versus polystyrene standards.  
(c) Significant amount of double molecular weight peak was detected. The PDI value includes the double molecular weight peak. (d) Incomplete polymerization.



Table 4. Tacticities of Polynorbornadienes Prepared Using Mo(NAr<sub>1</sub>)(CHCMe<sub>2</sub>Ph)(OR)<sub>2</sub> Initiators.

| Run | Monomer  | Aryl                | OR  | Solv  | equiv | time(h) | M <sub>n</sub> (found) <sup>a</sup> | PDI <sup>a</sup> | cis(%) | tacticity           |
|-----|--|---------------------|-----|---|-------|---------|-------------------------------------|------------------|--------|---------------------|
| 1   | (CF <sub>3</sub> ) <sub>2</sub> <sup>b</sup>   | (i-Pr) <sub>2</sub> | F6  | thf   | 200   | 5       | 45700                               | 1.10             | 98     | 75(mm)              |
| 2   |  |                     | F6  | tol   | 100   |         | 19500                               | 1.05             | 98     | 62(mm)              |
| 3   |  |                     | F6  | tol(10thf)                                    | 100   |         | 18600                               | 1.12             | 98     | 60(mm)              |
| 4   |  |                     | F6  | tol(10MeCN)                                   | 100   |         | 15800                               | 1.06             | 98     | 57(mm)              |
| 5   |  |                     | F9  | tol   | 100   | 2       | 21100                               | 1.04             | 99     | 40(mm)              |
| 6   |  |                     | F9  | pentane                                       | 100   |         | 17300                               | 1.07             | 98     | 56(mm)              |
| 7   |  |                     | F9  | CF <sub>3</sub> C <sub>6</sub> H <sub>5</sub> | 100   |         | 16200                               | 1.04             | 99     | 53(mm)              |
| 8   |  |                     | F9  | CH <sub>2</sub> Cl <sub>2</sub>               | 100   |         | 13200                               | 1.04             | 99     | 59(mm)              |
| 9   |  |                     | F9  | DME   | 100   |         | 16700                               | 1.03             | 99     | 44(mm)              |
| 10  |  |                     | F13 | tol   | 40    | 4       | 6300                                | 1.08             | 95     | 77(ir)              |
| 11  |  | Me <sub>2</sub>     | F6  | tol   | 100   |         | 23200                               | 1.09             | 99     | 52(mm)              |
| 12  |  |                     | F9  | tol   | 100   |         | 11200                               | 1.07             | 99     | 85(mm)              |
| 13  |  |                     | F13 | tol   | 39    | 1       | 5400                                | 1.11             | 99     | 88(mm)              |
| 14  |  | t-Bu                | F9  | tol   | 100   | 0.4     | 18300                               | 1.10             | 99     | 67(mm)              |
| 15  | (CO <sub>2</sub> Me) <sub>2</sub> <sup>c</sup> | (i-Pr) <sub>2</sub> | F6  | tol   | 100   |         | 16400                               | 1.04             | 98     | 60(mm)              |
| 16  |  |                     | F9  | tol   | 100   |         | 15400                               | 1.19             | 97     | 61(mm) <sup>d</sup> |
| 17  |  |                     | F13 | tol   | 100   |         | 14900                               | 1.20             | 99     | 54(mm)              |

|    |  |                        |     |     |       |      |    |        |
|----|--|------------------------|-----|-----|-------|------|----|--------|
| 18 | Me <sub>2</sub>                                  | F6                     | tol | 100 | 20100 | 1.16 | 96 | 52(mm) |
| 19 |  | F9                     | tol | 100 | 18900 | 1.17 | 99 | 71(mm) |
| 20 |  | F13                    | tol | 50  | 9900  | 1.12 | 99 | 69(mm) |
| 21 | (CO <sub>2</sub> Et) <sub>2</sub> <sup>e</sup>   | (i-Pr) <sub>2</sub> F9 | tol | 100 | 20200 | 1.26 | 97 | 71(mm) |
| 22 | (CO <sub>2</sub> i-Pr) <sub>2</sub> <sup>f</sup> | F9                     | tol | 100 | 11800 | 1.27 | 97 | 65(mm) |
| 23 | (CO <sub>2</sub> t-Bu) <sub>2</sub> <sup>g</sup> | F6                     | tol | 100 | 21300 | 1.15 | 99 | 88(mm) |
| 24 |  | F9                     | tol | 100 | 21700 | 1.16 | 99 | 95(mm) |
| 25 |  | F13                    | tol | 100 | 18700 | 1.42 | 99 | 90(mm) |

<sup>a</sup> By GPC viscometry employing refractometer data. <sup>b</sup> 100 mer MW = 23032, including end groups. <sup>c</sup> 100 mer MW = 21042, including end groups. <sup>d</sup> at 213 K, PDI = 1.09, 99% cis, 73%(mm). <sup>e</sup> 100 mer MW = 23822, including end groups. <sup>f</sup> 100 mer MW = 26652, including end groups. <sup>g</sup> 100 mer MW = 239462, including end groups.

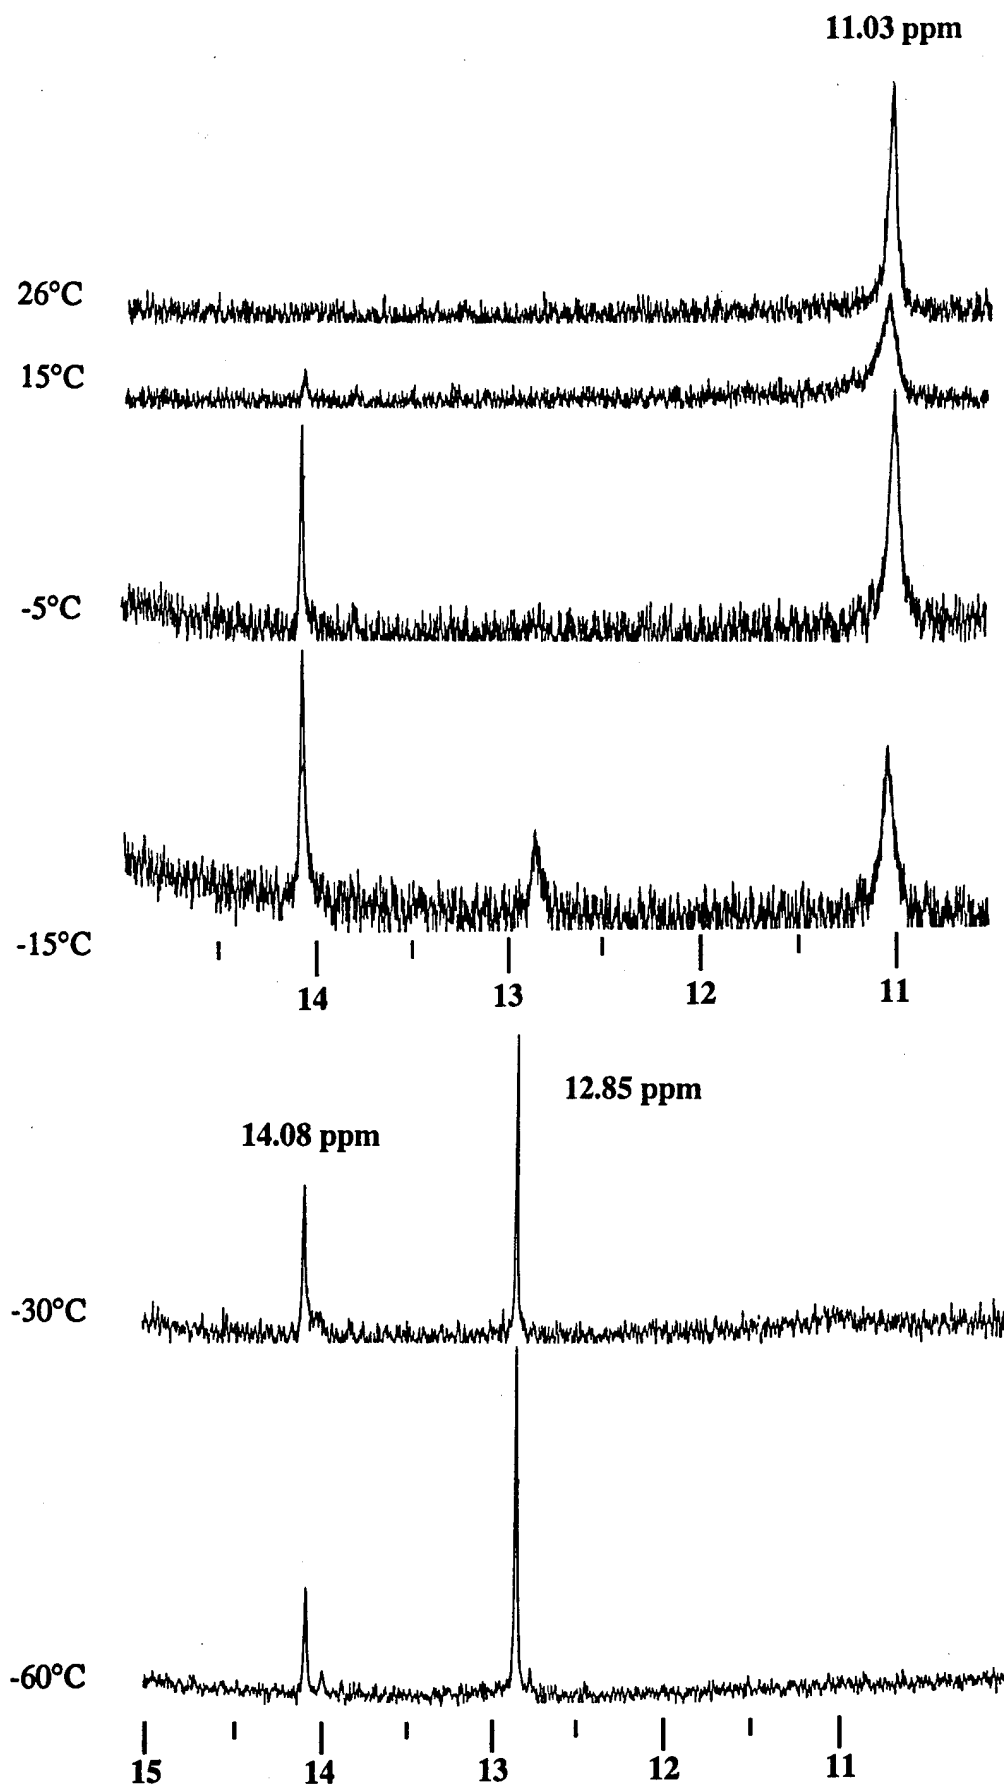
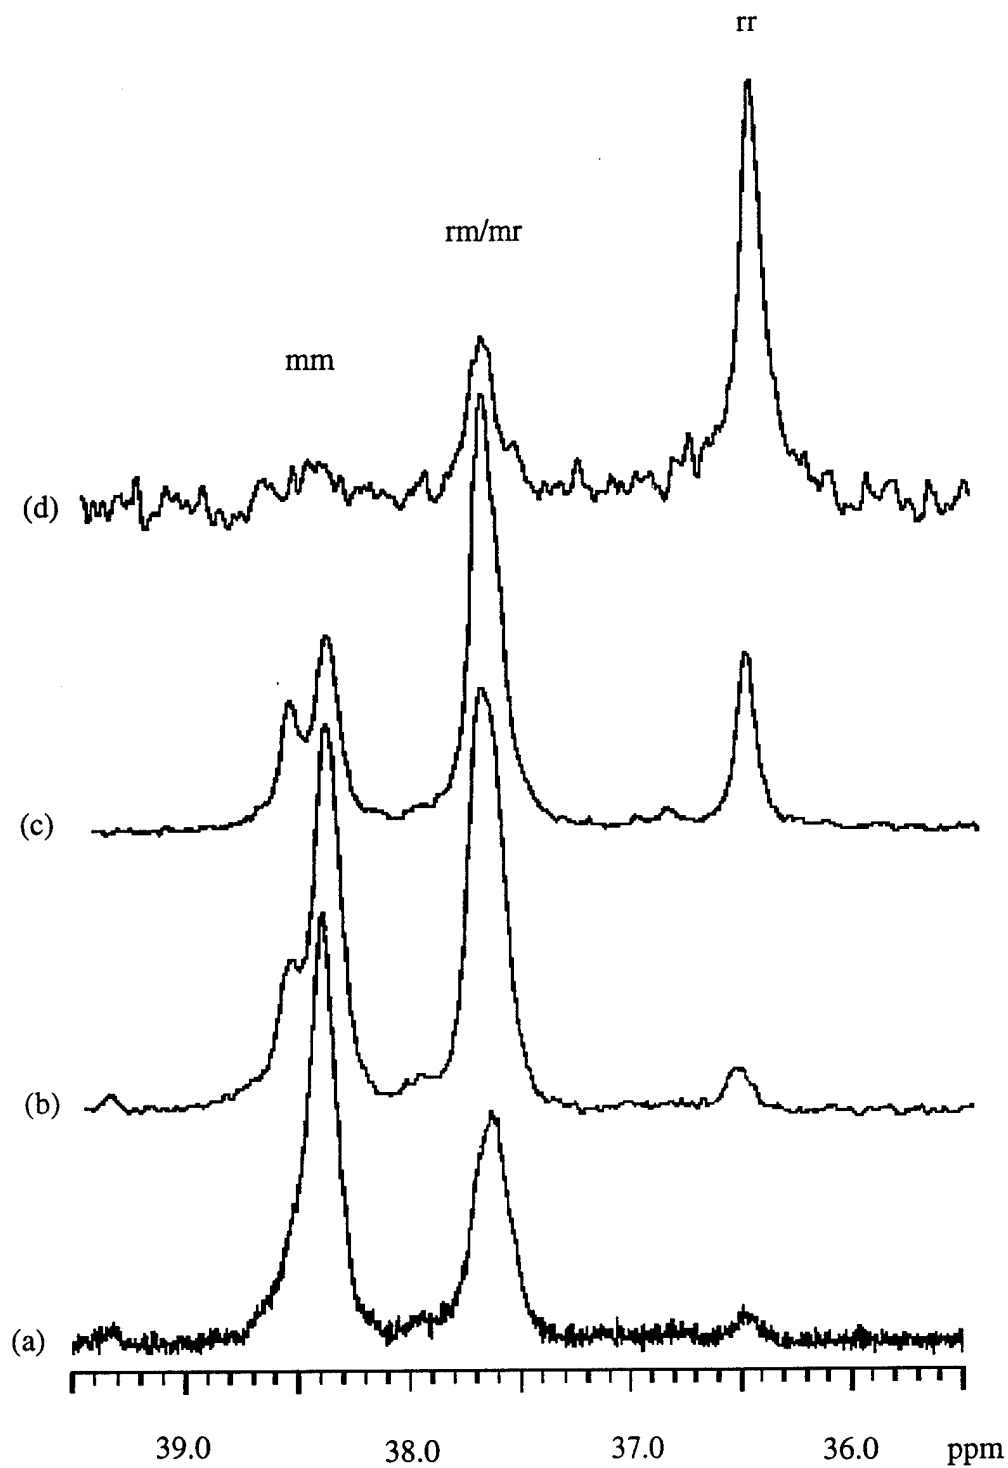


Figure 1. Proton NMR spectra of 1(THF) in the alkylidene H<sub>α</sub> region (in toluene-d<sub>8</sub>).



**Figure 2.** 125 MHz  $^{13}\text{C}$  NMR spectra of the methylene region (C7) region of high-cis poly(NBDF6) prepared in (a) run 1, (b) run 2, (c) run 5, and (d) run 10 in Table 4.

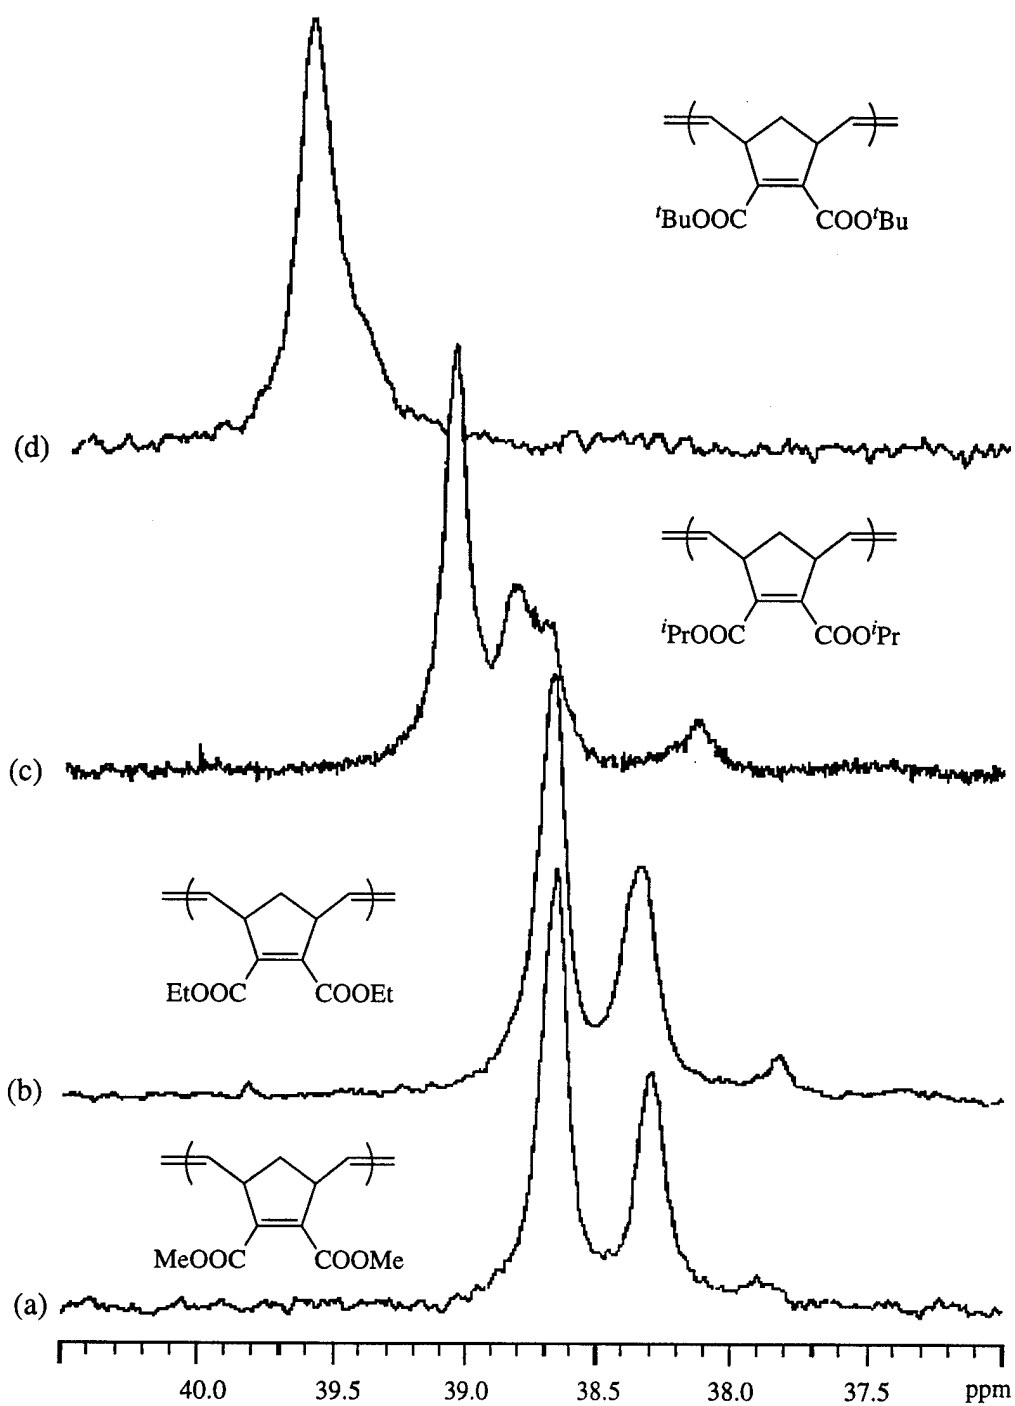


Figure 3. Four polymers prepared in (a) run 16, (b) run 21, (c) run 22, and (d) run 24; Table 4.

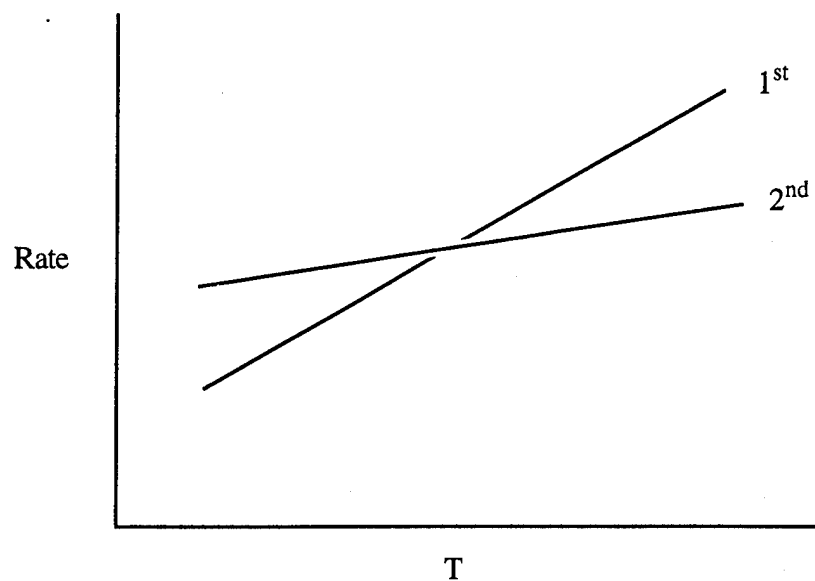


Figure 4. Possible relative temperature dependencies of the rate of second order chain growth versus first order rotamer interconversion.